
01 Jan 1999

Magnetic and Crystallographic Properties of $\text{LaNi}_{5-x}\text{Fex}$

C. Tan

Oran Allan Pringle

Missouri University of Science and Technology, pringle@mst.edu

Mingxing Chen

William B. Yelon

Missouri University of Science and Technology, yelonw@mst.edu

et. al. For a complete list of authors, see https://scholarsmine.mst.edu/phys_facwork/362

Follow this and additional works at: https://scholarsmine.mst.edu/phys_facwork

 Part of the [Chemistry Commons](#), and the [Physics Commons](#)

Recommended Citation

C. Tan and O. A. Pringle and M. Chen and W. B. Yelon and J. Gebhardt and N. Ali and C. Y. Tai and G. K. Marasinghe and G. D. Waddill and W. J. James, "Magnetic and Crystallographic Properties of $\text{LaNi}_{5-x}\text{Fex}$," *Proceedings of the 1999 IEEE International Magnetics Conference, 1999*, Institute of Electrical and Electronics Engineers (IEEE), Jan 1999.

The definitive version is available at <https://doi.org/10.1109/INTMAG.1999.837862>

This Article - Conference proceedings is brought to you for free and open access by Scholars' Mine. It has been accepted for inclusion in Physics Faculty Research & Creative Works by an authorized administrator of Scholars' Mine. This work is protected by U. S. Copyright Law. Unauthorized use including reproduction for redistribution requires the permission of the copyright holder. For more information, please contact scholarsmine@mst.edu.

MAGNETIC AND CRYSTALLOGRAPHIC PROPERTIES OF $\text{LaNi}_{1-x}\text{Fe}_x$

C. Y. Tai, C. Tan, G. K. Marasinghe, G. D. Waddill, O. A. Pringle, and W. J. James
 Departments of Physics and Chemistry and the Graduate Center for Materials Research,
 University of Missouri-Rolla, Rolla, MO 65409
 Mingxing Chen and W. B. Yelon
 Research Reactor, University of Missouri-Columbia, Columbia, MO 65211
 Jeffrey Gebhardt and Naushad Ali
 Department of Physics, Southern Illinois University at Carbondale, Carbondale, IL 62901

Rare earth-iron intermetallics are still the best candidates for the next generation of economically feasible high performance permanent magnetic materials. In spite of several decades of research dedicated to understanding the magnetic interactions in these materials, several aspects remain poorly understood. Recent developments¹ in spin resolved photoemission spectroscopy provide an opportunity to investigate, in unprecedented detail, a poorly understood aspect, the relationship between the electronic band structure and the bulk and microscopic magnetic properties. However, interpretation of spin-resolved photoemission spectra of complex intermetallics is very difficult. Consequently, it is prudent to first study a relatively simple system such as RM_3 (R-rare earth, M-transition metal), which is the building block of more complex intermetallics such as RM_{12} and R_2M_{17} . Because RFe_3 intermetallics do not exist, one must study an iron doped RM_3 system such as $\text{LaNi}_{1-x}\text{Fe}_x$, in order to obtain information about the contribution from the iron sub-lattice to the band structure.

For best results, it is desirable to study samples with large amounts of iron. Iron concentrations of samples used in early studies² of $\text{LaNi}_{1-x}\text{Fe}_x$ were limited to about $x=1.2$ but concentrations as high as $x=1.5$ have been recently achieved³ using somewhat tedious processing techniques. Herein, we report the crystallographic and magnetic properties of a series of induction melted $\text{LaNi}_{1-x}\text{Fe}_x$ ($0 \leq x \leq 1.4$) samples intended for spin-resolved photoemission analysis. The information presented in this paper will be crucial to the success of the planned spin-resolved photoemission studies.

$\text{LaNi}_{1-x}\text{Fe}_x$ samples were prepared from 99.99 percent pure elements by induction melting in a cold copper crucible followed by annealing at 950°C for 120 hours. The phase purity of the samples was checked by x-ray diffraction with Cu K_α radiation on a Scintag XDS 2000 x-ray diffractometer equipped with a single crystal graphite monochromator. The bulk magnetic properties of the samples were measured at the Southern Illinois University-Carbondale on a Quantum Design SQUID magnetometer. The powder neutron diffraction data were obtained at the University of Missouri Research Reactor for samples placed in thin-walled vanadium containers and exposed to 1.4875 Å neutrons for 4-6 hours each at 30 and 295 K. The spectra were refined by the Rietveld technique.

Corresponding Author: G. K. Marasinghe
 101 Materials Research Center
 University of Missouri-Rolla
 Rolla, MO 65409
 USA
 Phone: 573 341 4873, Fax: 573 341 2071
 E-Mail: gkmars@umr.edu

Figure 1 shows thermo-magnetic data for three of the samples. The data for $x=1$ and for $x=1.2$ sample are in good agreement with prior work.² Increasing the iron content from $x=1.2$ to $x=1.35$ increases the Curie temperature by another 25 degrees. However, saturation magnetization is affected only marginally by the same change in the iron concentration.

Neutron diffraction patterns for all of the samples could be fit based on the CaCu_3 type structure (space group $\text{P } 6/\text{mmm}$). Figure 2 shows the neutron diffraction pattern measured at 30 K for $\text{LaNi}_{3.65}\text{Fe}_{1.35}$ along with a fit based on the CaCu_3 type structure. The unit cell expands isotropically with increasing iron content such that the cell volume of $\text{LaNi}_{3.65}\text{Fe}_{1.35}$ is 3.4% larger than that of LaNi_5 . Refined occupancy factors indicate that approximately 90% of the iron atoms occupy the 3g transition metal site.

Analysis of bulk magnetization data and magnetic moments obtained from neutron diffraction data reveals that Ni atoms possess a induced magnetic moment.

The authors acknowledge the financial support of the National Science Foundation for grant DMR-9614596 and the Defense Advanced Research Projects Agency for grant DAAG 55-98-1-0267.

¹ J.P. Woods, B. M. Patterson, A. S. Fernando, and S. S. Jaswal, Phys. Rev. B **51**, 1064 (1995).

² J. Lamlouni, A. Percheron-Guegan, J. C. Achard, G. Jehanno, and D. Givord, J. Physique **45**, 108 (1984)

³ M. Gerlach, N. Mommer, M. Hirscher, and H. Kronmüller, J. Alloys Compounds **267**, 47 (1998).

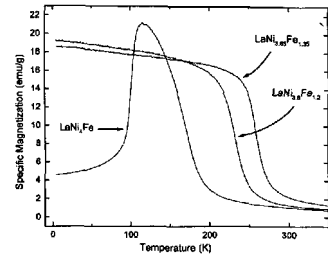


Fig. 1. Thermo-magnetic data for selected $\text{LaNi}_{1-x}\text{Fe}_x$ samples.

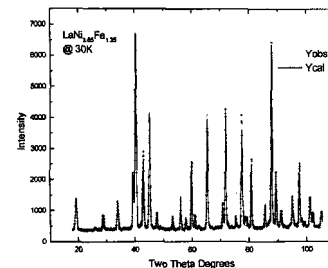


Fig. 2. Neutron diffraction pattern measured at 30 K for $\text{LaNi}_{3.65}\text{Fe}_{1.35}$ and a fit based on the CaCu_3 structure.